



# TEST REPORT

ACCORDING TO IES LM-80-2015

For

## Hongli Zhihui Group Co.,Ltd. Guangzhou Branch

Room 316, Building 2, No.1, Xianke Yi Road, Huadong Town, Huadu District, Guangzhou, China

**Model: HL-AS-2835DVW-2C-**

FINVA

**Note:** The test data was only valid for the test sample(s). This test report is prepared for the customer shown above and for the device described herein. It may not be duplicated or used in part without prior written consent from Bay Area Compliance Laboratories Corp. (Dongguan).  
This report is valid only with a valid digital signature. The digital signature may be available only under the Adobe software above version 7.0.

## TABLE OF CONTENTS

<b>1 -</b>	<b>General Information .....</b>	<b>3</b>
1.1	Description of LED Light Sources .....	3
1.2	Standards Used: .....	8
1.3	Testing Equipment .....	8
1.4	Drive Level.....	8
1.5	Ambient Conditions for Maintenance Test.....	8
1.6	Measurement Uncertainty .....	9
1.7	Statement of Traceability.....	9
1.8	Sample Set.....	10
<b>2 -</b>	<b>Summary of Test Result .....</b>	<b>11</b>
<b>3 -</b>	<b>Test Data .....</b>	<b>12</b>
3.1	Data Set 1, 55°C, 60mA (Lumen Maintenance) .....	12
3.2	Data Set 1, 55°C, 60mA (Forward Voltage) .....	13
3.3	Data Set 1, 55°C, 60mA (Chromaticity Shift) .....	14
3.4	Data Set 2, 105°C, 60mA (Lumen Maintenance) .....	15
3.5	Data Set 2, 105°C, 60mA (Forward Voltage) .....	16
3.6	Data Set 2, 105°C, 60mA (Chromaticity Shift) .....	17
<b>4 -</b>	<b>EUT Photo.....</b>	<b>18</b>
4.1	Mechanical Dimensions.....	18
4.2	EUT Photo .....	18
	<b>Report Revision.....</b>	<b>19</b>



Model type	Model name	CRI (typ.)	CCT (typ.)	Series	Parallel	Power density (W/mm <sup>2</sup> )	Current density per LED die (mA/mm <sup>2</sup> )	Current per die (mA)	Distance between of dies	Current (mA)
Multiple models	HL-AS-2835HVW-2C-S1-08-PCT-HR3	80	>2200K	2	1	0.0566	132.10	30	0.15	30

FINAL

Model type	Model name	CRI (typ.)	CCT (typ.)	Series	Parallel	Power density (W/mm <sup>2</sup> )	Current density per LED die (mA/mm <sup>2</sup> )	Current per die (mA)	Distance between of dies	Current (mA)
Multiple models	HL-AS-2835DVW-S1-08-PCT-HR3	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-PU2835DVW-S1-08-PCT-HR3(R9)	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-PU2835DVW-S1-08-PCT-HR3	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-2835DVW-S1-08L-PCT-HR3(R9)	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-2835DVW-S1-08L-PCT-HR3	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-PU2835DVW-S1-08L-PCT-HR3(R9)	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-PU2835DVW-S1-08L-PCT-HR3	80	>2200K	1	1	0.0582	105.20	30	/	30
Multiple models	HL-AS-2835VDW-S1-08-PCT-HR3(R9)	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-2835VDW-S1-08-PCT-HR3	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-PU2835VDW-S1-08-PCT-HR3(R9)	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-PU2835VDW-S1-08-PCT-HR3	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-2835VDW-S1-08L-PCT-HR3(R9)	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-2835VDW-S1-08L-PCT-HR3	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-AS-PU2835VDW-S1-08L-PCT-HR3(R9)	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-A-PU2835VDW-S1-08L-PCT-HR3	80	>2200K	1	1	0.0582	134.78	30	/	30
Multiple models	HL-A-2835DVW-2C-S1-08-PCT-HR3(R9)	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-2835DVW-2C-S1-08-PCT-HR3	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-PU2835DVW-2C-S1-08-PCT-HR3(R9)	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-PU2835DVW-2C-S1-08-PCT-HR3	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-2835DVW-2C-S1-08L-PCT-HR3(R9)	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-2835DVW-2C-S1-08L-PCT-HR3	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-PU2835DVW-2C-S1-08L-PCT-HR3(R9)	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-PU2835DVW-2C-S1-08L-PCT-HR3	80	>2200K	2	1	0.1163	272.73	60	0.15	60
Multiple models	HL-A-2835HVW-2C-S1-08-PCT-HR3(R9)	80	>2200K	2	1	0.0566	132.10	30	0.15	30
Multiple models	HL-A-2835HVW-2C-S1-08-PCT-HR3	80	>2200K	2	1	0.0566	132.10	30	0.15	30

Model type	Model name	CRI (typ.)	CCT (typ.)	Series	Parallel	Power density (W/mm <sup>2</sup> )	Current density per LED die (mA/mm <sup>2</sup> )	Current per die (mA)	Distance between of dies	Current (mA)
Multiple models	HL-A-PU2835HVW-2C-S1-08-PCT-HR3(R9)	80	>2200K	2	1	0.0566	132.10	30	0.15	30

FINAL



## 1.2 Standards Used:

IESNA LM-80-15: IES Approved Method for Measuring Lumen Maintenance of LED Light Sources.

ENERGY STAR® Requirements for the Use of LM-80 Data (This standard was not accredited by IAS)

## 1.3 Testing Equipment

Device	Manufacture	Model No	Serial No	Test Range	Calibration date	Calibration due date
0.3m integrating sphere	EVERFINE	Diameter 0.3m	1011119	0.3m		

FINAL



During life testing,  $TMP_{LED}$  of the coldest LEDs were maintained at a temperature that was greater than or equal to  $2^{\circ}\text{C}$  below the corresponding nominal case temperature. Surrounding air was maintained at a temperature that was greater than or equal to  $5^{\circ}\text{C}$  below the corresponding nominal case temperature. Thermocouples were shielded from direct DUT optical radiation and c

Samples were connected to DC power supply in series circuits with a constant current. The forward current was regulated to within  $\pm 3\%$  of the specified value of the manufacturer.

The relative humidity within chamber was kept less than 65% during test.

For photometry measurement, the ambient temperature during test was set to  $25^{\circ}\text{C} \pm 2^{\circ}\text{C}$ , RH <65%.

## **1.6 Measurement Uncertainty**

The uncertainty of the light output measurements is  $U=1.59\%$  ( $K=2$ ), at the 95% confidence level. The uncertainty of the correlated color temperature measurements is  $U=21\text{K}$  ( $K=2$ ), at the 95% confidence level.

The uncertainty of the temperature is  $U=0.8671^{\circ}\text{C}$  ( $K=2$ ), at the 95% confidence level.

## **1.7 Statement of Traceability**

Bay Area Compliance Laboratories Corp. (Dongguan) attested that all calibration has been performed using suitable standards traceable to National Primary Standards and International System of Units (SI).

## 1.8 Sample Set

### Data Set 1: 55°C, 60mA

Part Number: HL-AS-2835DVW-2C-S1-08-PCT-HR3 (R9)  
Number of Units: 25  
Case Temperature: >53°C  
Ambient Temperature: >50°C  
Life Test Drive Current: 60mA  
Measurement Current: 60mA

### Data Set 2: 105°C, 60mA

Part Number: HL-AS-2835DVW-2C-S1-08-PCT-HR3 (R9)  
Number of Units: 25  
Case Temperature: >103°C  
Ambient Temperature: >100°C  
Life Test Drive Current: 60mA  
Measurement Current: 60mA

## 2 - Summary of Test Result

Data Set:	Sample Size	Failures Observed:	Test Interval(hours)	Test Duration(hours)	Reported TM-21 L <sub>70</sub> Lifetime
1	25	0	1000	9000	>54000hours
2	25	0	1000	9000	>54000hours

### Average Lumen Maintenance (Percentage of Initial Luminous Flux)

Data Set:	1000	2000	3000	4000	5000	6000	7000	8000	9000
1	100.28%	100.11%	99.93%	99.72%	99.51%	99.33%	99.10%	98.87%	98.64%
2	99.82%	99.52%	99.22%	98.88%	98.61%	98.33%	98.04%	97.78%	97.49%

### Average Color Maintenance

Data Set:	1000	2000	3000	4000	5000	6000	7000	8000	9000
1	0.0003	0.0007	0.0009	0.0013	0.0015	0.0018	0.0020	0.0025	0.0026
2	0.0005	0.0008	0.0012	0.0015	0.0018	0.0019	0.0022	0.0023	0.0028

### 3 - Test Data

#### 3.1 Data Set 1, 55°C, 60mA (Lumen Maintenance)

No.	Ohr(Initial)	Lumen Maintenance (%)								
		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs	7000hrs	8000hrs	9000hrs
1	127.9	100.23	100.08	99.92	99.61	99.37	99.30	99.06	98.75	98.51
2	128.1	100.23	100.16	99.92	99.77	99.53	99.38	99.06	98.91	98.67
3	125.9	100.32	100.24	100.16	99.92	99.68	99.52	99.21	99.05	98.73
4	131.8	100.08	99.85	99.77	99.70	99.39	99.32	99.09	98.94	98.86
5	127.2	100.39	100.24	99.92	99.76	99.61	99.29	98.98	98.74	98.43
6	131.8	100.38	100.15	99.85	99.54	99.32	99.24	99.09	98.86	98.63
7	131.4	100.30	99.85	99.77	99.54	99.24	99.01	98.78	98.55	98.33
8	130.2	100.08	99.92	99.69	99.62	99.31	99.16	98.85	98.54	98.16
9	133.2	100.30	100.15	99.92	99.70	99.55	99.40	99.32	99.25	98.95
10	129.4	100.31	100.08	99.92	99.85	99.61	99.54	99.38	99.15	99.00
11	127.2	100.39	100.24	100.08	99.76	99.53	99.14	98.98	98.90	98.66
12	129.5	100.31	100.15	99.92	99.77	99.46	99.23	99.00	98.69	98.61
13	134.4	100.37	100.22	100.15	99.93	99.70	99.33	99.03	98.81	98.66
14	131.1	100.15	100.08	99.85	99.62	99.47	99.24	99.01	98.86	98.55
15	126.5	100.32	100.16	100.08	99.92	99.84	99.68	99.45	99.21	99.05
16	132.5	100.38	100.15	99.92	99.70	99.40	99.25	99.09	98.79	98.49
17	128.1	100.39	100.23	100.08	99.77	99.53	99.38	99.14	98.99	98.67
18	129.4	100.31	100.15	99.85	99.61	99.46	99.38	99.23	98.92	98.69
19	134.6	100.37	100.22	99.93	99.63	99.41	99.26	99.03	98.74	98.51
20	126.9	100.32	100.24	100.16	99.84	99.68	99.45	99.29	99.05	98.82
21	131.7	100.15	99.77	99.70	99.54	99.32	99.09	98.86	98.63	98.41
22	131.0	100.23	100.08	99.92	99.77	99.47	99.31	99.01	98.93	98.70
23	129.4	100.39	100.23	100.15	99.85	99.77	99.69	99.46	99.23	99.07
24	133.2	100.08	99.85	99.70	99.55	99.40	99.25	98.95	98.57	98.42
25	122.2	100.33	100.16	99.92	99.84	99.67	99.43	99.18	98.77	98.45
Ave.	129.8	100.28	100.11	99.93	99.72	99.51	99.33	99.10	98.87	98.64
Med.	129.5	100.31	100.15	99.92	99.76	99.47	99.31	99.06	98.86	98.66
st dev	2.9426	0.1039	0.1435	0.1449	0.1245	0.1567	0.1643	0.1785	0.2051	0.2288
Min.	122.2	100.08	99.77	99.69	99.54	99.24	99.01	98.78	98.54	98.16
Max.	134.6	100.39	100.24	100.16	99.93	99.84	99.69	99.46	99.25	99.07

TM-21 Projection:

**Test Duration:** 9000 hours  
**Failures Observed:** 0  
 2.175E-06  
 1.006  
**Reported L<sub>70</sub>:** >54000 hours



### 3.3 Data Set 1, 55°C, 60mA (Chromaticity Shift)

No.			CCT(K)										
	0hr(Initial)			1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs	7000hrs	8000hrs	9000hrs	
1	0.2572	0.5289	2806	0.0003	0.0008	0.0010	0.0012	0.0015	0.0019	0.0020	0.0023	0.0026	
2	0.2605	0.5323	2721	0.0004	0.0007	0.0010	0.0011	0.0012	0.0017	0.0021	0.0022	0.0025	
3	0.2585	0.5296	2775	0.0004	0.0007	0.0010	0.0014	0.0013	0.0018	0.0022	0.0023	0.0027	
4	0.2553	0.5308	2839	0.0003	0.0007	0.0009	0.0014	0.0015	0.0016	0.0023	0.0025	0.0026	
5	0.2571	0.5279	2812	0.0002	0.0006	0.0009	0.0013	0.0015	0.0015	0.0021	0.0024	0.0025	
6	0.2568	0.5323	2799	0.0004	0.0007	0.0009	0.0013	0.0015	0.0014	0.0021	0.0025	0.0027	
7	0.2573	0.5278	2808	0.0004	0.0009	0.0011	0.0015	0.0018	0.0021	0.0026	0.0029	0.0030	
8	0.2577	0.5287	2796	0.0006	0.0010	0.0014	0.0019	0.0022	0.0026	0.0029	0.0034	0.0035	
9	0.2557	0.5299	2833	0.0003	0.0006	0.0007	0.0012	0.0013	0.0016	0.0016	0.0021	0.0021	
10	0.2567	0.5279	2822	0.0003	0.0007	0.0009	0.0012	0.0013	0.0016	0.0016	0.0021	0.0021	
11	0.2575	0.5290											

BDC q361.03 542.3

FINAL

### 3.4 Data Set 2, 105°C, 60mA (Lumen Maintenance)

No.	Ohr(Initial)	Lumen Maintenance (%)								
		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs	7000hrs	8000hrs	9000hrs
26	136.5	99.85	99.56	99.34	99.12	98.83	98.68	98.39	98.02	97.73
27	129.5	99.77	99.54	99.31	99.00	98.76	98.53	98.38	98.15	97.92
28	124.3	99.84	99.36	99.03	98.79	98.47	98.15	97.99	97.91	97.83
29	133.0	99.85	99.47	99.02	98.72	98.35	98.20	97.82	97.44	97.22
30	127.3	99.76	99.45	99.14	98.74	98.43	98.27	97.80	97.49	97.25
31	130.7	99.77	99.46	99.08	98.85	98.55	98.09	97.86	97.48	97.25
32	127.7	99.84	99.45	99.14	98.67	98.43	98.04	97.81	97.65	97.34
33	130.3	99.92	99.62	99.39	98.93	98.70	98.39	98.08	98.00	97.70
34	128.3	99.92	99.53	99.22	99.06	98.67	98.36	98.13	97.97	97.74
35	132.4	99.77	99.47	98.94	98.56	98.34	98.19	97.89	97.51	97.36
36	129.8	99.92	99.69	99.46	99.08	98.92	98.69	98.46	98.00	97.69
37	130.0	99.85	99.62	99.31	99.00	98.62	98.38	98.08	97.69	97.31
38	127.1	99.84	99.53	99.37	99.13	98.90	98.66	98.51	98.19	97.88
39	128.6	99.84	99.46	99.14	98.91	98.68	98.37	97.90	97.74	97.43
40	127.2	99.76	99.45	99.37	98.98	98.58	98.27	97.88	97.48	97.25
41	128.6	99.69	99.46	99.30	98.99	98.83	98.52	98.13	97.90	97.59
42	129.9	99.85	99.38	99.00	98.77	98.69	98.23	98.00	97.77	97.54
43	134.2	99.78	99.63	99.18	98.66	98.36	98.06	97.62	97.47	97.17
44	130.7	99.77	99.46	99.23	99.01	98.62	98.39	98.09	98.01	97.63
45	132.4	99.85	99.62	99.32	99.02	98.64	98.41	98.04	97.89	97.66
46	132.4	99.92	99.55	99.17	98.72	98.41	98.11	97.89	97.51	97.05
47	128.7	99.77	99.69	99.38	98.91	98.60	98.29	98.06	97.82	97.51
48	129.0	99.84	99.53	99.30	98.76	98.53	98.22	97.91	97.67	97.36
49	128.9	99.69	99.46	99.07	98.76	98.53	98.14	97.98	97.75	97.36
50	128.0	99.84	99.61	99.38	98.98	98.83	98.52	98.28	97.89	97.58
Ave.	129.8	99.82	99.52	99.22	98.88	98.61	98.33	98.04	97.78	97.49
Med.	129.5	99.84	99.53	99.23	98.91	98.62	98.29	98.00	97.77	97.51
st dev	2.6042	0.0661	0.0895	0.1439	0.1591	0.1731	0.1932	0.2237	0.2300	0.2385
Min.	124.3	99.69	99.36	98.94	98.56	98.34	98.04	97.62	97.44	97.05
Max.	136.5	99.92	99.69	99.46	99.13	98.92	98.69	98.51	98.19	97.92

TM-21 Projection:

**Test Duration:** 9000 hours  
**Failures Observed:** 0  
2.831E-06  
1.000  
**Reported L<sub>70</sub>:** >54000 hours

### 3.5 Data Set 2, 105°C, 60mA (Forward Voltage)

No.	Forward Voltage (V)									
	0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs	7000hrs	8000hrs	9000hrs
26	18.70	18.76	18.68	18.70	18.69	18.67	18.65	18.68	18.66	18.69
27	18.85	18.90	18.82	18.83	18.82	18.80	18.78	18.82	18.80	18.82
28	18.82	18.86	18.79	18.80	18.78	18.77	18.76	18.78	18.76	18.79
29	18.63	18.67	18.60	18.60	18.59	18.58	18.57	18.59	18.57	18.59
30	18.85	18.89	18.81	18.81	18.80	18.79	18.79	18.80	18.80	18.81
31	18.85	18.89	18.80	18.81	18.80	18.80	18.80	18.80	18.79	18.81
32	18.81	18.84	18.76	18.77	18.76	18.77	18.76	18.77	18.76	18.79
33	18.72	18.75	18.68	18.68	18.67	18.68	18.67	18.68	18.68	18.70
34	18.69	18.72	18.66	18.67	18.65	18.65	18.64	18.65	18.67	18.67
35	18.84	18.89	18.80	18.81	18.80	18.80	18.78	18.80	18.81	18.82
36	18.76	18.80	18.72	18.72	18.71					


FINAL






## 4 - EUT Photo

### 4.1 Mechanical Dimensions

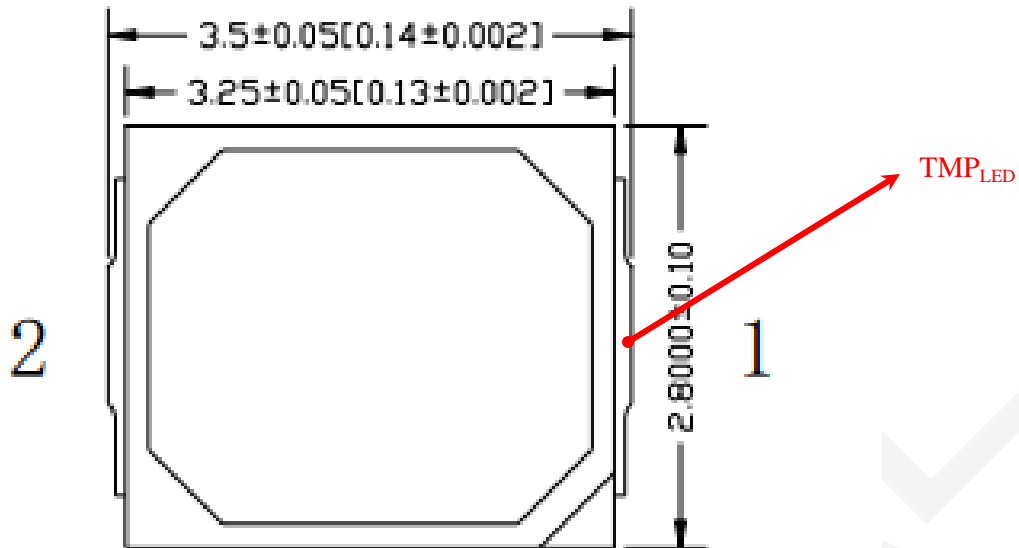

All dimensions are in millimeter

### 4.2 EUT Photo

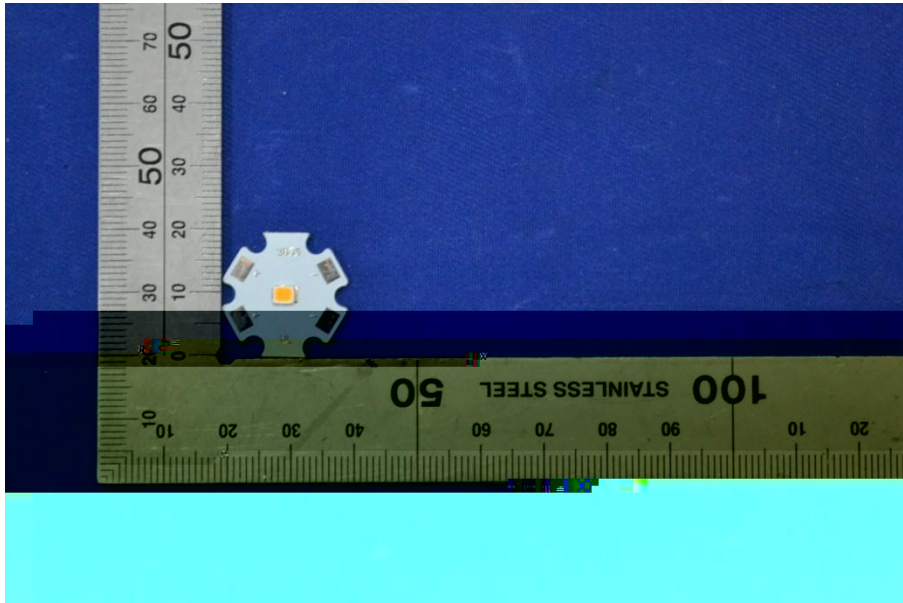

## Report Revision

---

Report Number	Report Date	Contents
RSZ161122518-10-9000	2017-12-22	Original report.
RSZ161122518-10-9000-M1	2018-03-26	Update the data of Power Density per LED die in page 3.
RSZ161122518-10-9000-M2	2019-01-14	Update the Logo of lab on the Page1 Update Company name and address on page 1.

\*\*\*\*\*END OF REPORT\*\*\*\*\*

FINAL